

Mercuric Iodide - Photocorrosion Resistant Semiconductor

K. TENNAKONE

*Department of Physics, University of Ruhuna, Matara, Sri Lanka**(Date of receipt: 23 May 1984)**(Date of acceptance: 27 November 1984)*

Abstract: n - Mercuric Iodide with layer crystal structure is found to resist photocorrosion when used as the anode in photoelectrochemical cells.

1. Introduction

In recent literature, a great deal of attention is given to photoelectrochemical cells as promising devices for conversion and/or storage of solar energy.^{4,9} The advantages of these systems is that the insensitivity of the photoresponse to defects and impurities in the semiconductor - polycrystalline and amorphous materials give results comparable to single crystal slices.^{8,11} However, they are plagued with photocorrosion. Most semiconductors show a noticeable rate of photocorrosion even if best possible redox electrolytes are used.^{6,7} Recently it has been found that semiconducting materials with layered crystal structure (e.g. MoS₂, WSe₂) strongly resist photocorrosion.¹² In this note we report our observations on photocorrosion resistance of red mercuric iodide which is known to have a layered crystal structure.¹⁴

2. Experimental

Red HgI₂ (α) has a layer structure with HgI₂²⁻ tetrahedra linked the vertices.¹⁴ The α -phase is stable up to 400° K.¹⁴ Above this temperature, the yellow HgI₂ (β) is more stable. Red HgI₂ behaves as a n - type semiconductor of band gap 2.37 eV.^{2,10} In all experiments analytical grade (BDH brand) HgI₂ is used. HgI₂ made by double decomposition of mercuric chloride with potassium iodide gives identical results.

The photoanode is made by depositing HgI₂ on a platinum foil by vacuum sublimation at ~ 423°K. The yellow form which is deposited reverts to the red α -phase few minutes after cooling to the room temperature. The counterelectrode used is a Pt foil and the electrolyte is 0.1 mol dm⁻³ solution of sodium sulphate. The time development (cathode illuminated at ~ 40 Wm⁻² from a mercury lamp) of the open circuit voltage V_{oc} and the short circuit current density (J_{sc}) is given in Figure 1. V_{oc} and J_{sc} remain practically constant demonstrating the photostability of HgI₂.

3. Results

Oxygen evolution can be seen at the photoanode. In the presence of atmospheric oxygen the cell operates in the photogalvanic mode where O₂ reduction instead of H₂ evolution takes place at the cathode. When the electrolyte is purged with

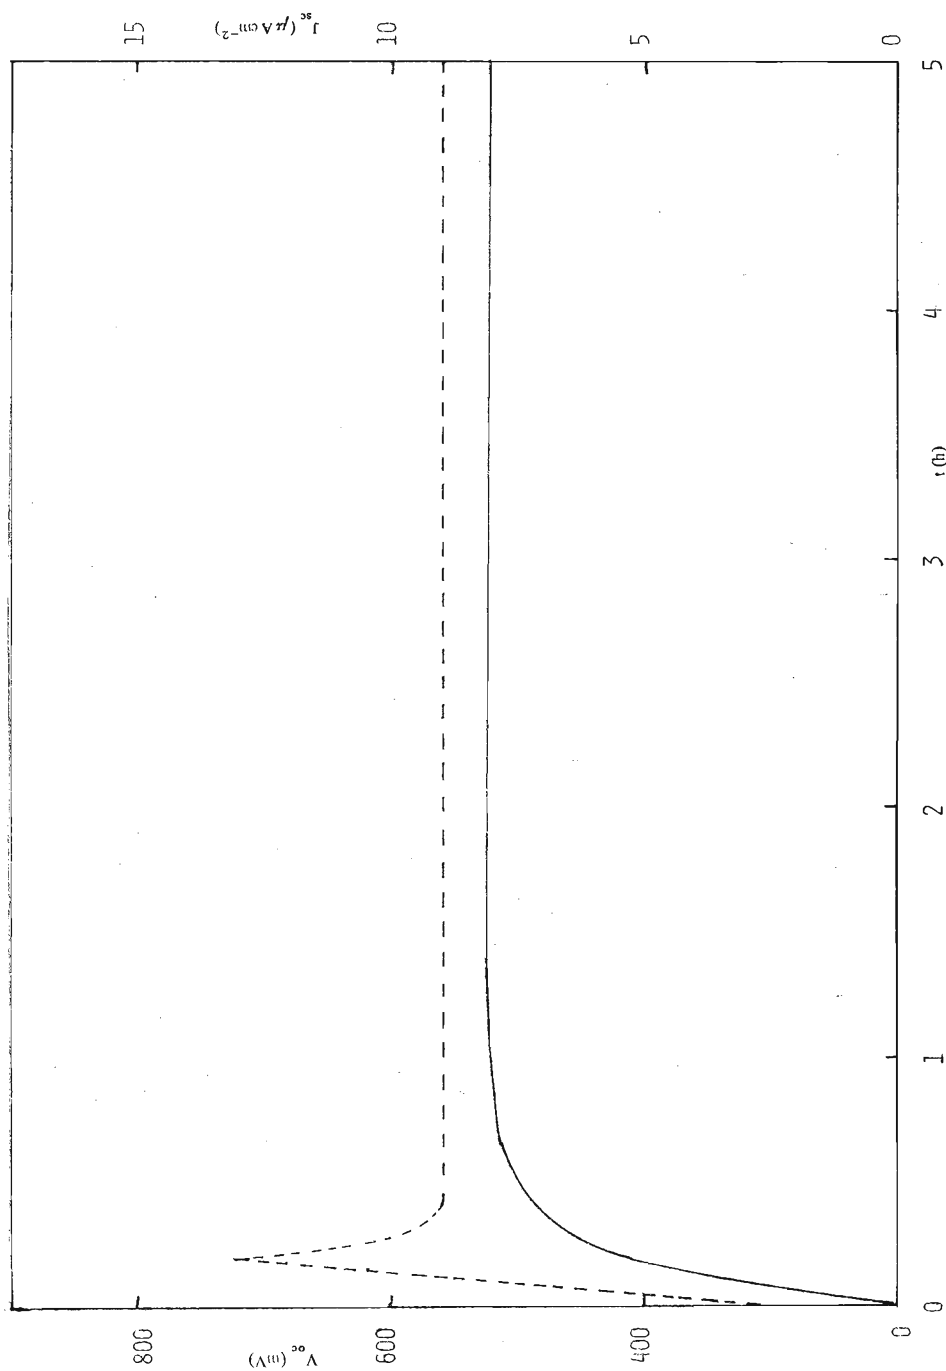


FIGURE 1. --- The plots of V_{oc} vs t (continuous line) and J_{sc} vs t (broken line) when the cathode is illuminated at $40 Wm^{-2}$ from a mercury lamp.

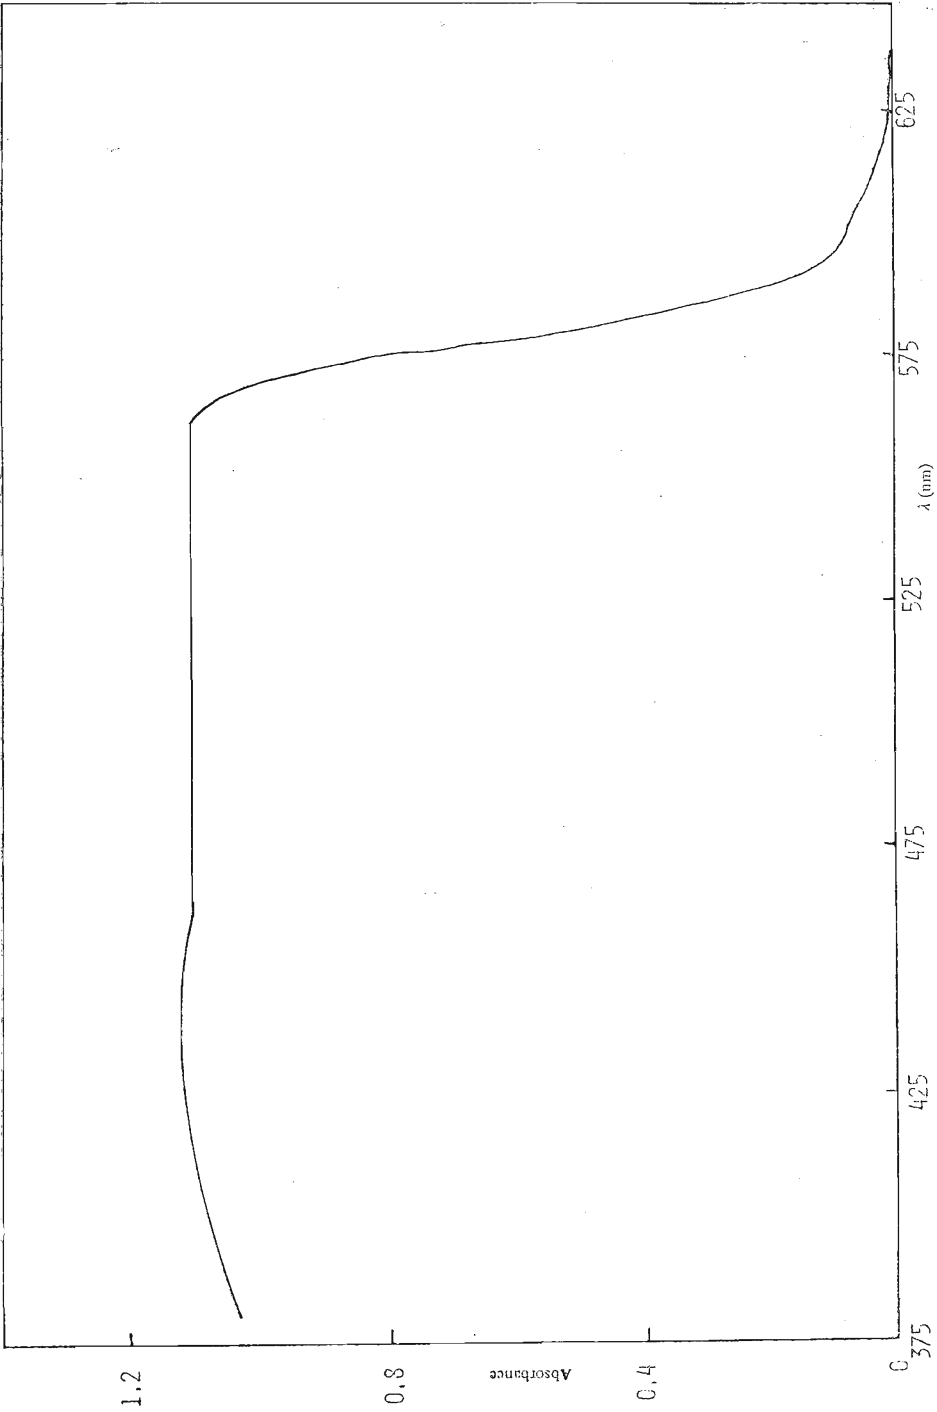


Figure 2 — Diffuse reflectance spectrum of HgI₂.

N_2 , H_2 evolution is seen only when the cell is externally biased. This indicates that H_2O/H_2 redox energy level is lying above the conduction band.⁵

The diffuse reflectance spectrum of polycrystalline HgI_2 powder (measured with a Unicamp Series II (Spectrophotometer) is shown in Figure 2. It is interesting to note the strong and almost constant absorption peak starting at ~ 600 nm.

References

1. ADDUCI, F., CINGOLANI, A., FERRERA, M., LUGARA, M. & MINFRA, A. (1977). *J. App. Phys.* **48**, 342.
2. ADDUCI, F., BALDASSARRI, L. & MINATRA, A. (1978). *J. App. Phys.* **49**, 6179.
3. BARD, A. J. & WRIGHTON, M. S. (1977). *J. Electrochem. Soc.* **124**, 1706.
4. BOLTON, J. R. & HALL, D. O. (1979). *Annual Reviews of Energy*, **4**, 353.
5. GERISCHER, H. & PHYSIK, Z. (1961). *Chem. (Frankfurt)* **27**, 48.
6. GERISCHER, H. (1977). *J. Electronal Chem.* **82**, 133.
7. KOHL, P. A. & BARD, A. J. (1979). *J. Electrochem. Soc.* **126**, 603.
8. MATSUMURA, M., NOMBURA, Y. & TSUBOMURA, H. (1979). *Bull. Chem. Soc. Jpn.* **52**, 1559.
9. MAVROIDES, J. G. (1977). *Mat. Res. Bull* **13**, 1379.
10. MINDER, R., OTTAVIANI, G. & CANALI, G. C. (1976). *J. Phys. Chem. Solids.* **37**, 417.
11. PETER, L. (1982) In *Light, Chemical change and life*, eds J. D. Coyle, R. R. Hill and D. R. Roberts (The Open University Press).
12. TRIBUTSCH, H. (1979). *Solar Energy Mater.* **1**, 257.
13. TSUBOMURA, H., MATSUMURA, M., NAKATANI, K., YAMAMOTO, K. & MEDA, K. (1978) *Solar Energy*, **21**, 93.
14. WELLS, A. F. (1975). *Structural Inorganic Chemistry* (Clarendon Press) pp. 326-376, chap. 9.